

**Reference X-Ray Spectra  
of  
Metal Foils**




**Exafs  
Materials**

871 El Cerro Blvd., Danville, CA 94526 USA Tel: (925) 838-7162




### ***Reference X-ray Spectra of Metal Foils***

The x-ray spectra compiled herein for the following metal foils were recorded at synchrotron beamlines 1-5, 4-2, 7-3 and 10-2 at Stanford Synchrotron Radiation Laboratory (SSRL) using double crystal Si(220) monochromators. The spectra for Ag, Pt and Au were recorded with a double crystal Si(111) monochromator on beamline X-11A at the National Synchrotron Light Source (NSLS) at Brookhaven. All spectra were taken at room temperature in the transmission geometry. In the region  $\pm 50$  eV about the absorption edge, each spectrum was scanned in step sizes 0.5 eV. An entrance slit with vertical opening of 1 mm and 0.5 mm was used for Si(220) and Si(111), respectively. The spectrometer resolution in each case was estimated to be 0.5 eV at the K-edge of Ti, and  $\sim 1.5$  eV at the K-edge of Cu. For each element, the tabulated edge energy (Bearden & Burr, *Rev. Mod. Phys.* 39, 125 (1967)) is defined operationally as the first inflection point in the derivative spectrum.




3d Metals:	Ti, V, Cr, Mn, Fe, Co, Ni, Cu, Zn, Se,
4d Metals:	Zr, Nb, Mo, Pd, Ag, Sn, Sb
5d Metals:	Ta, Pt, Au, Pb.

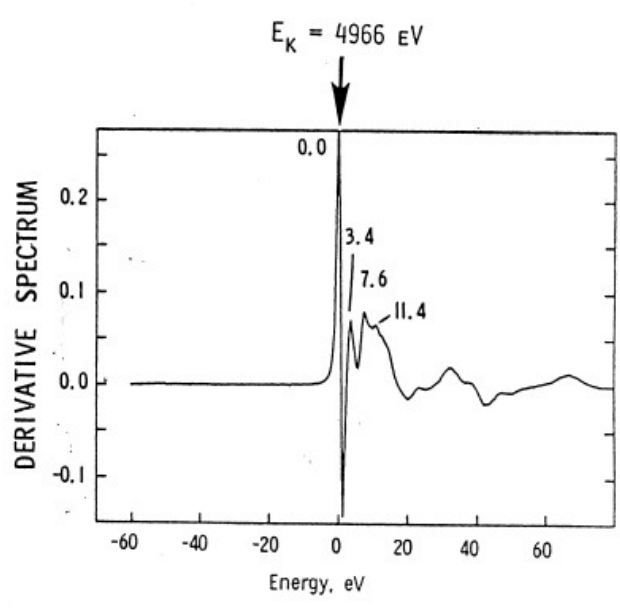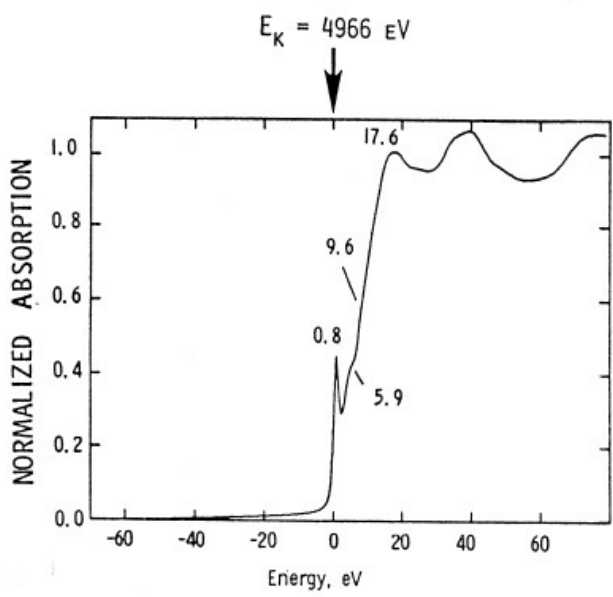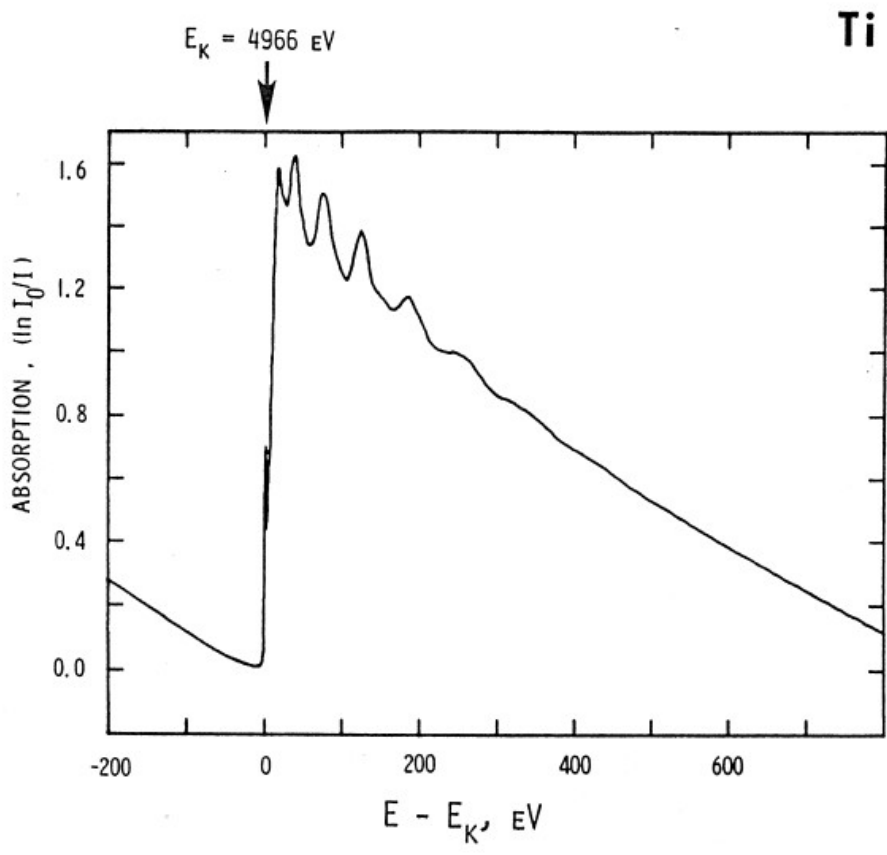


V

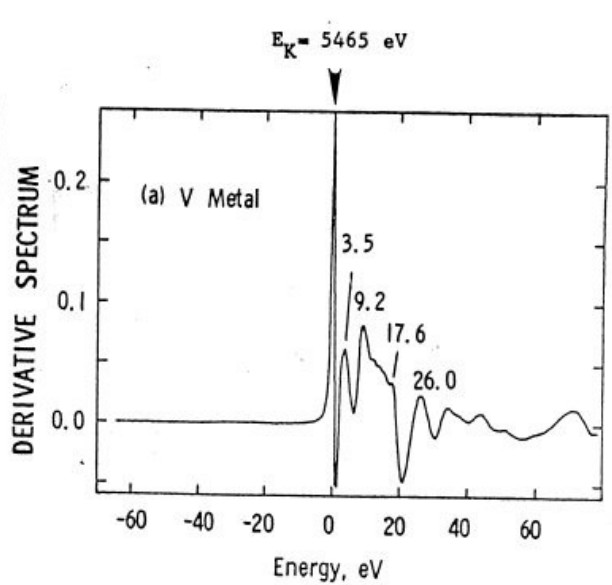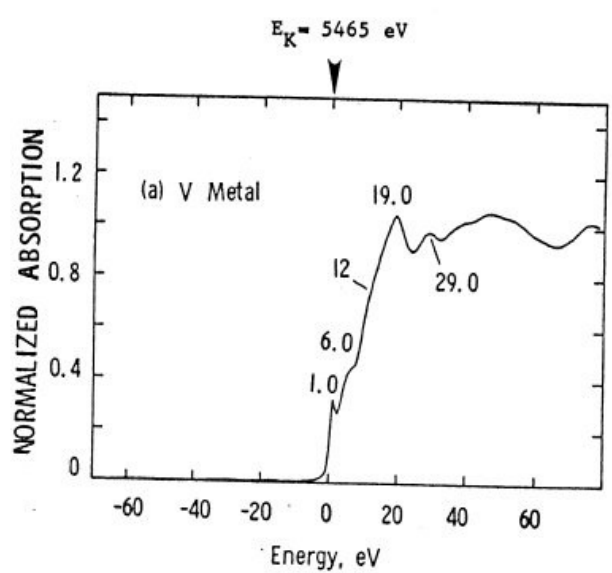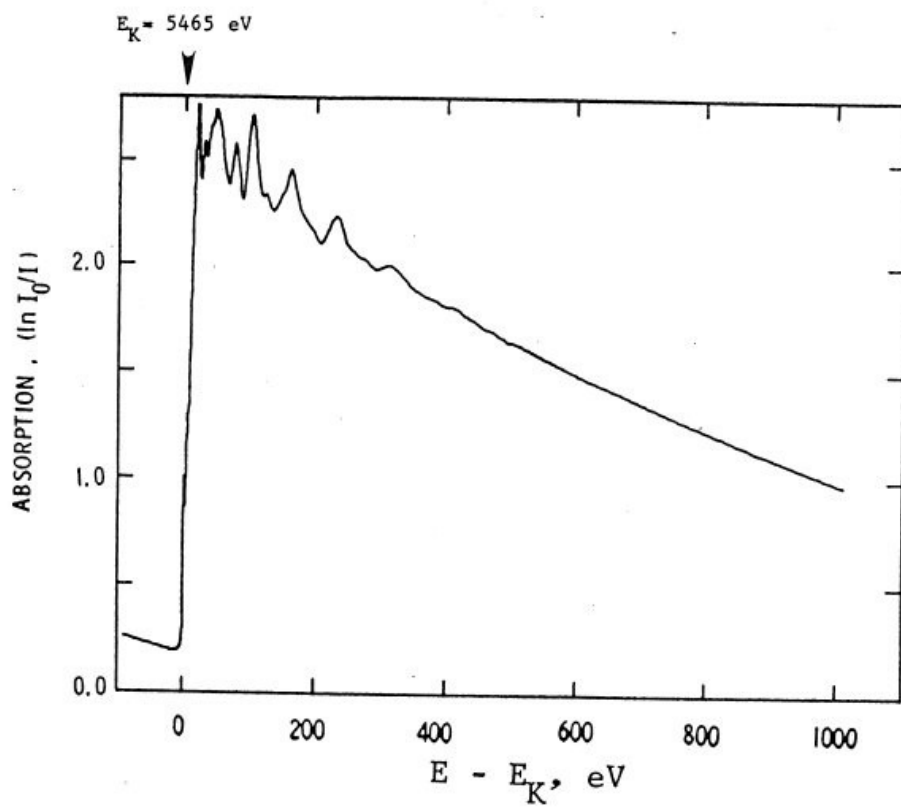



Cr

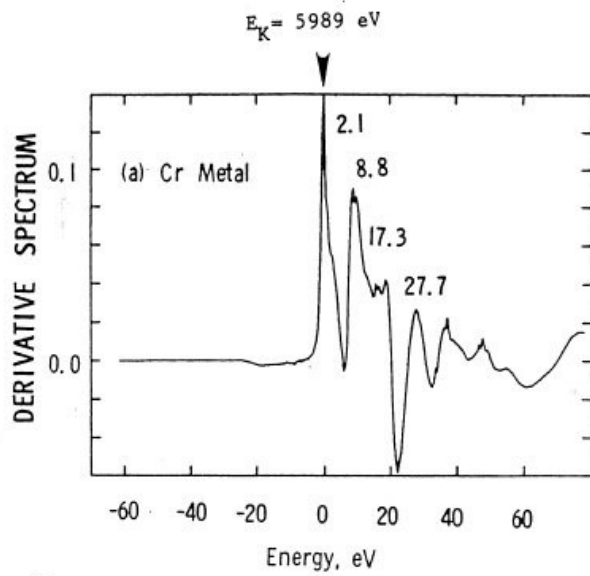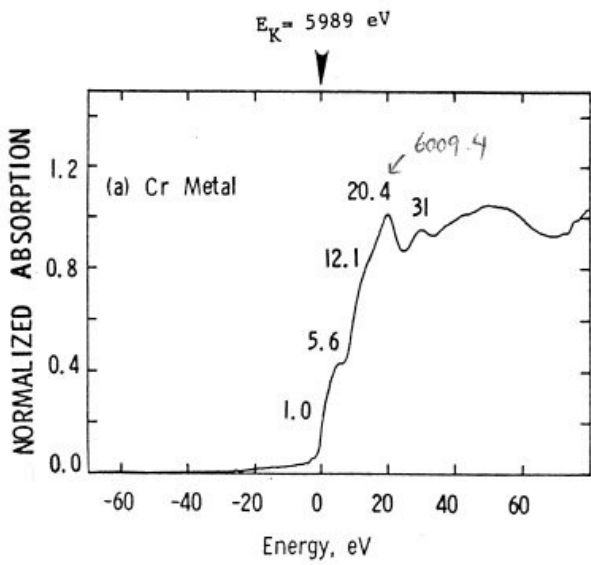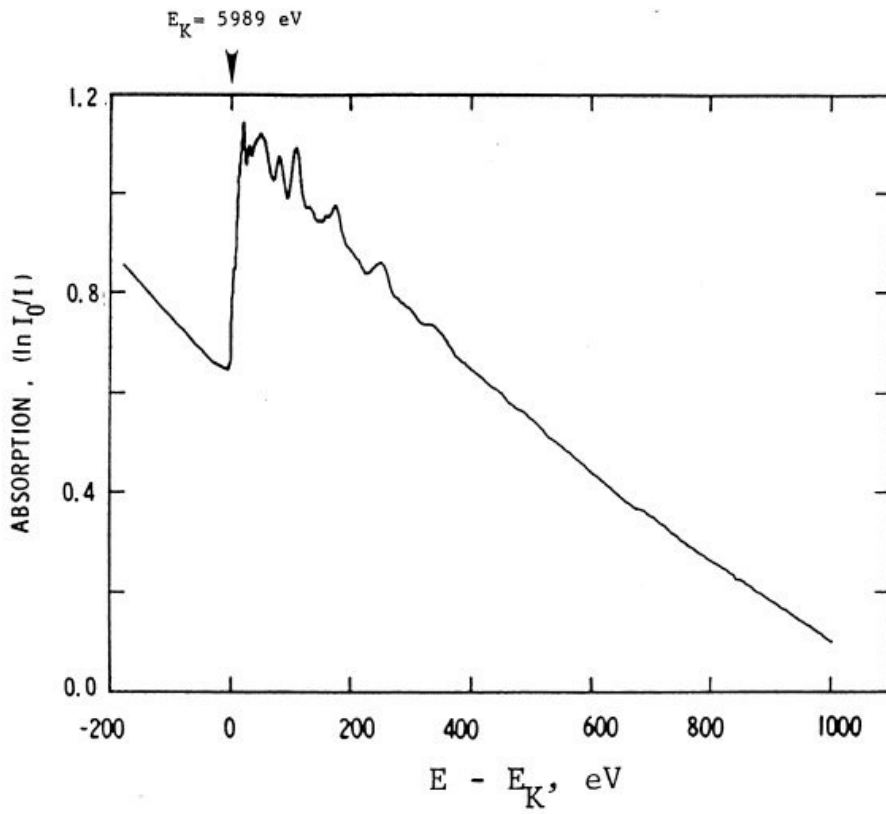




# Mn

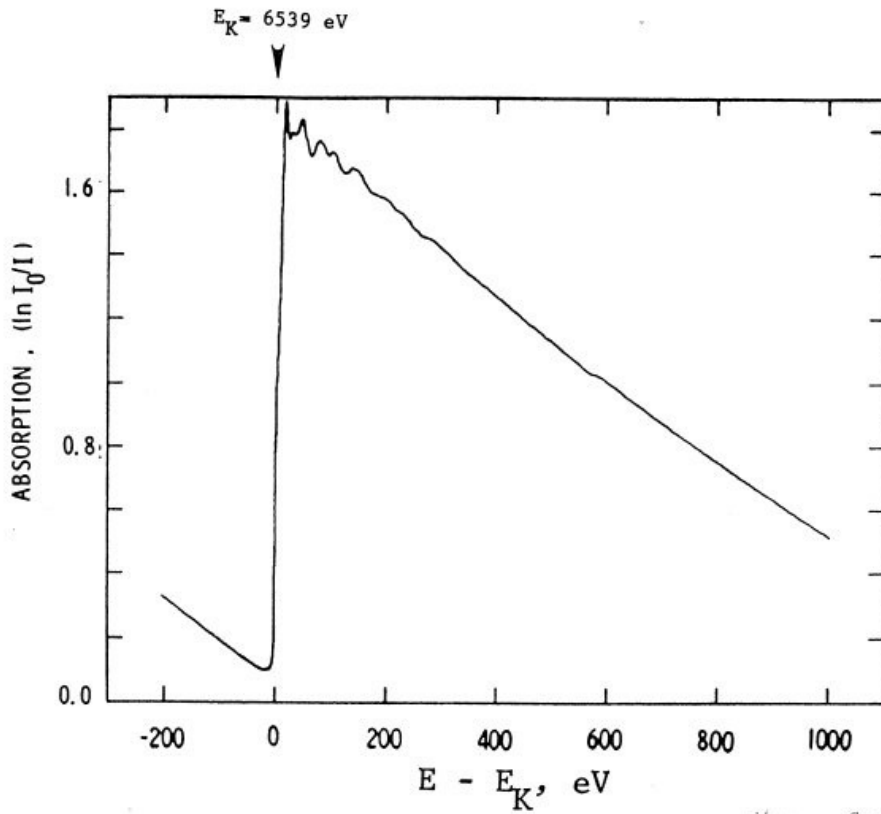




*this seems too thick 11108 CG.*

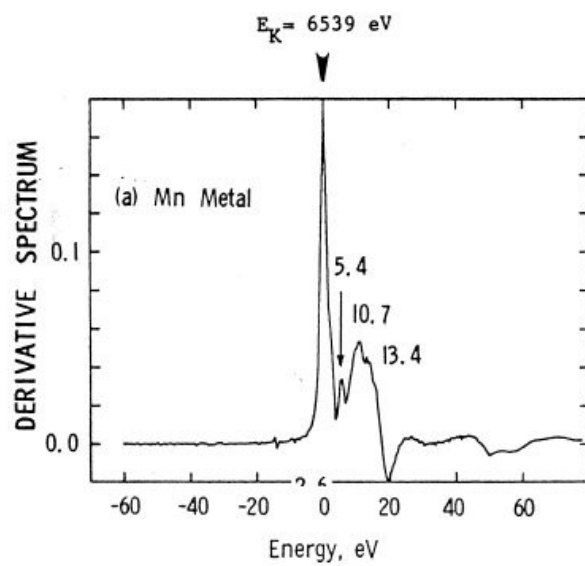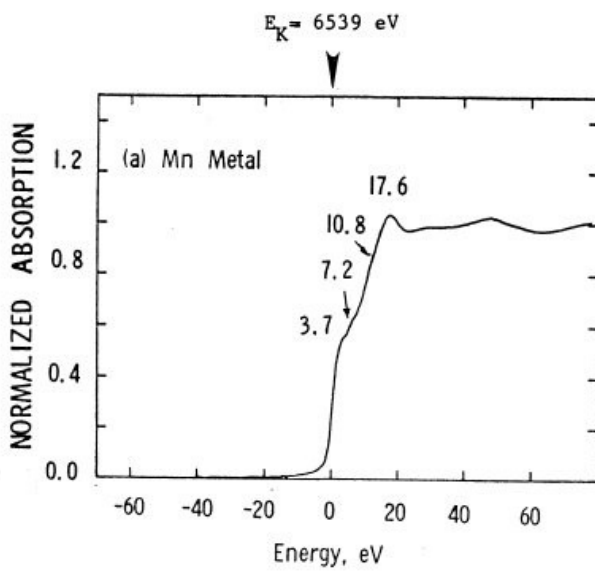

**Fe**

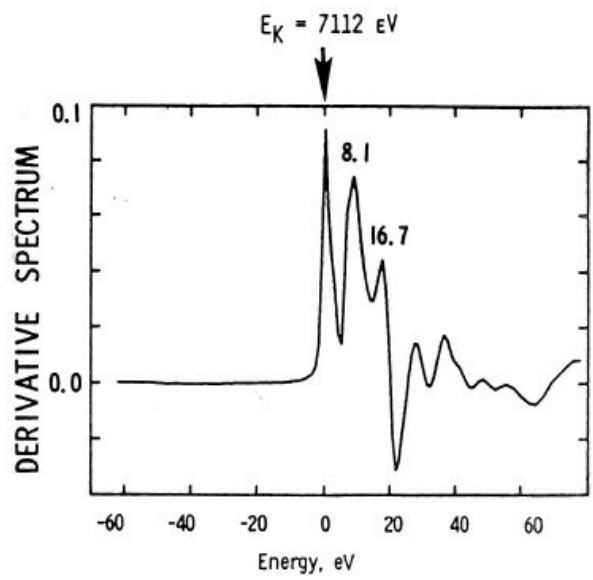
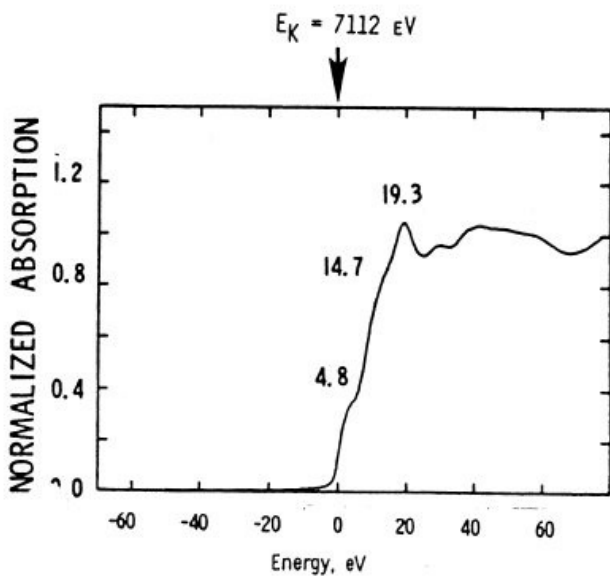
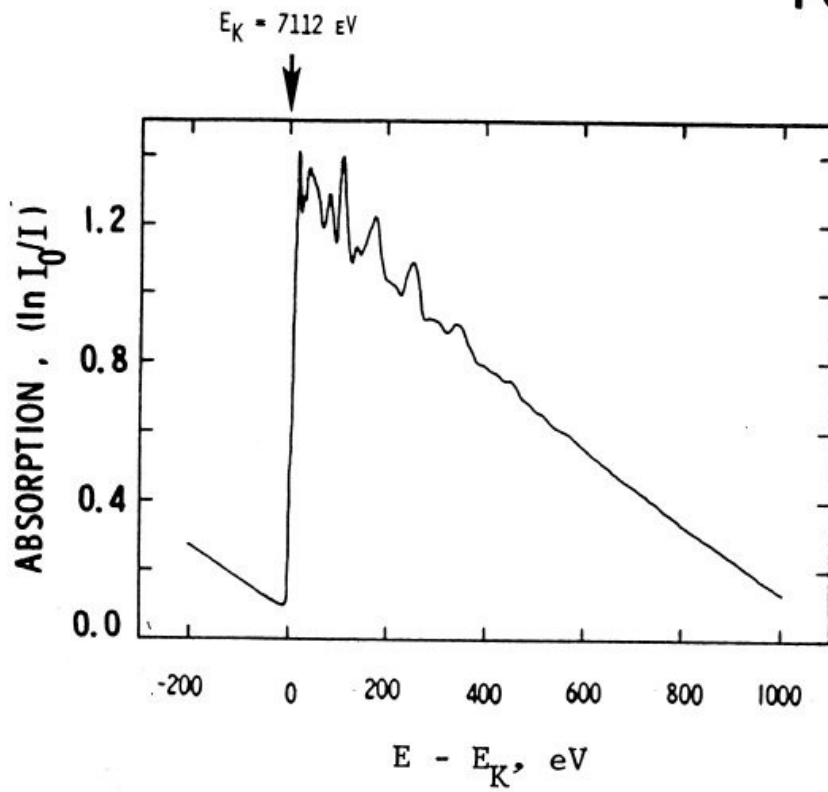


Co

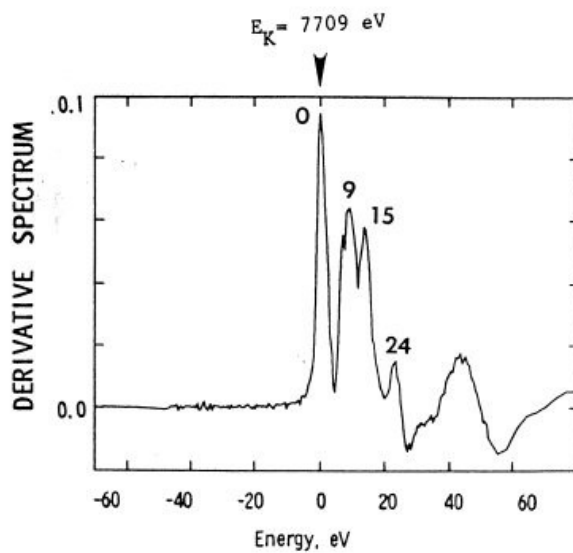
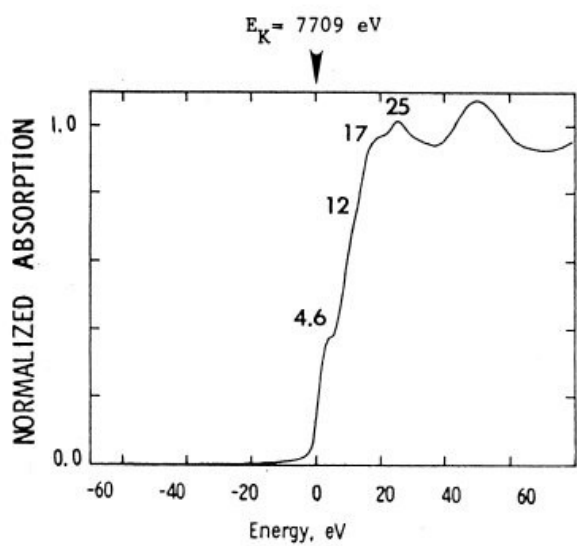
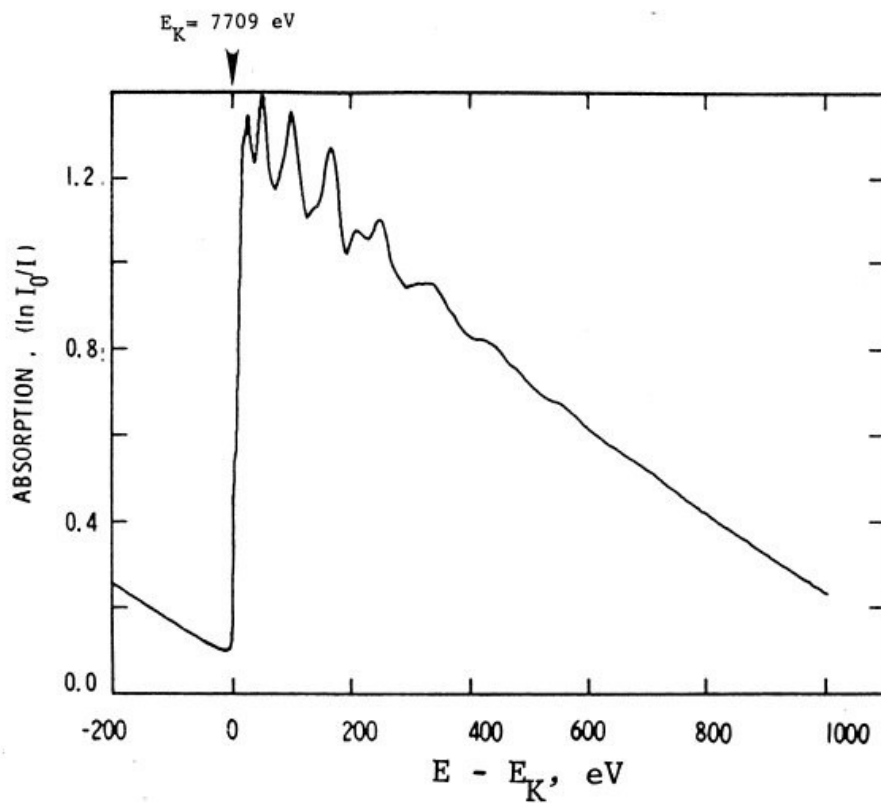







Ni

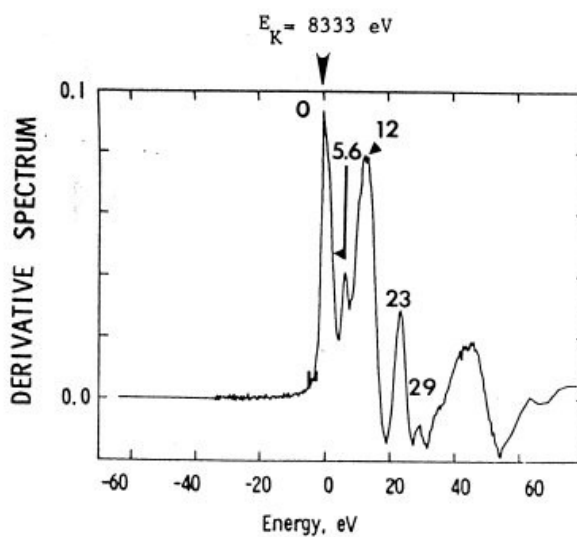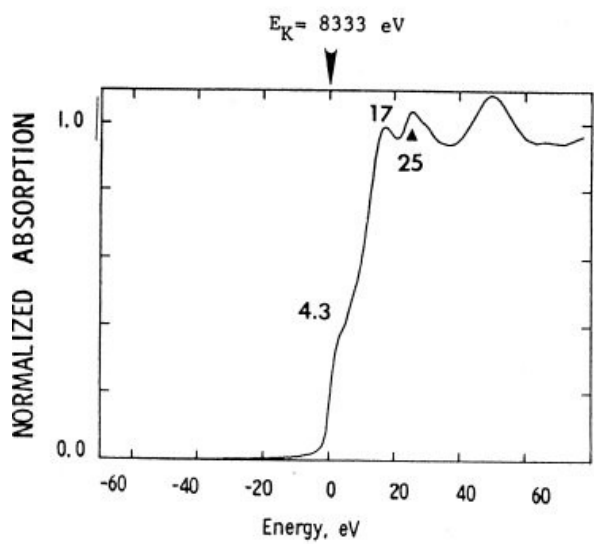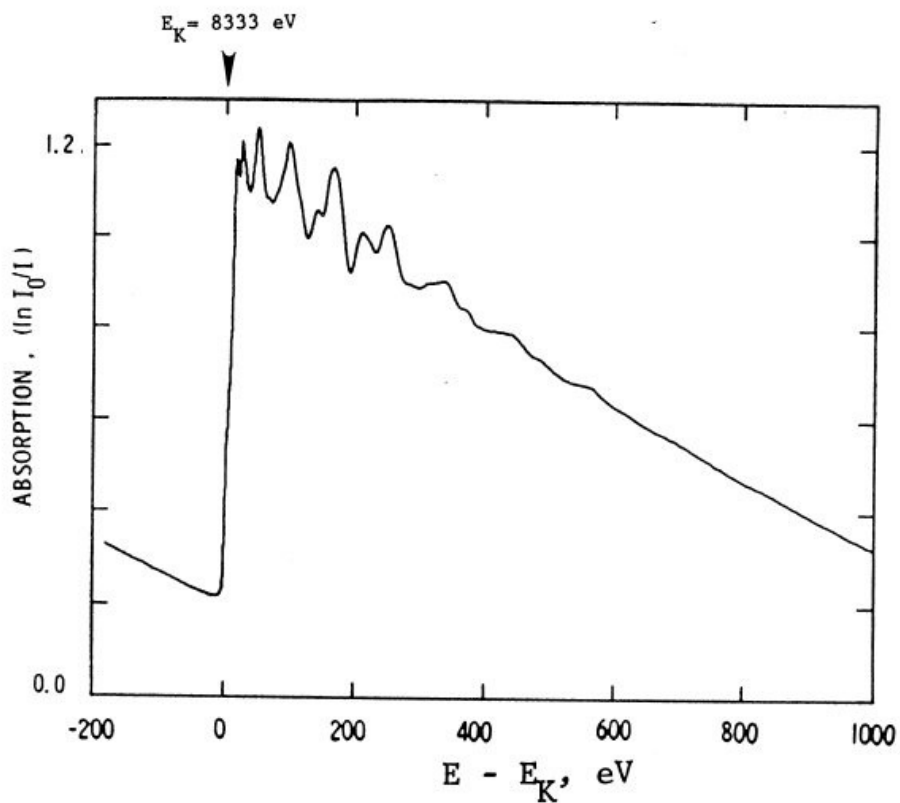




Cu

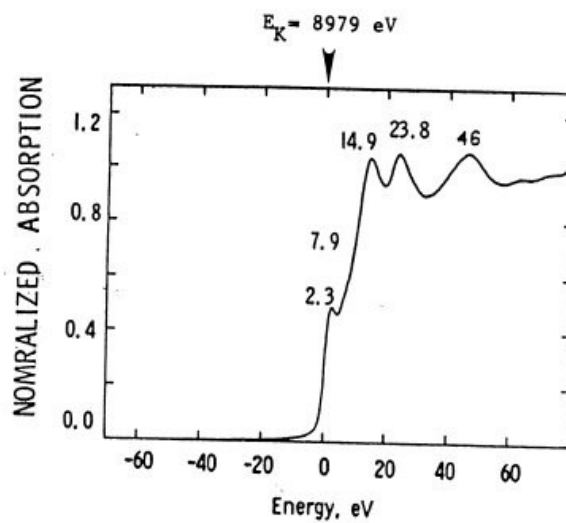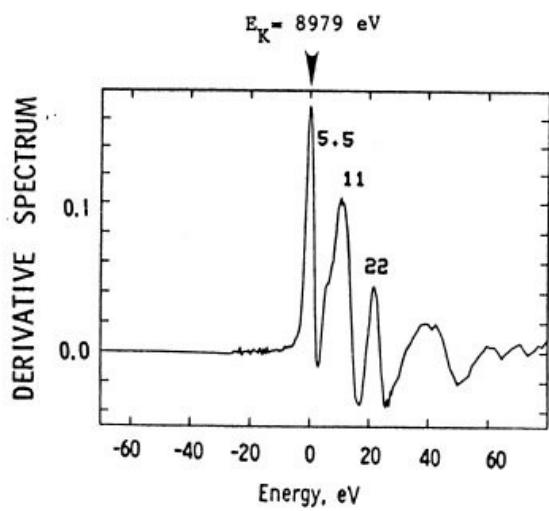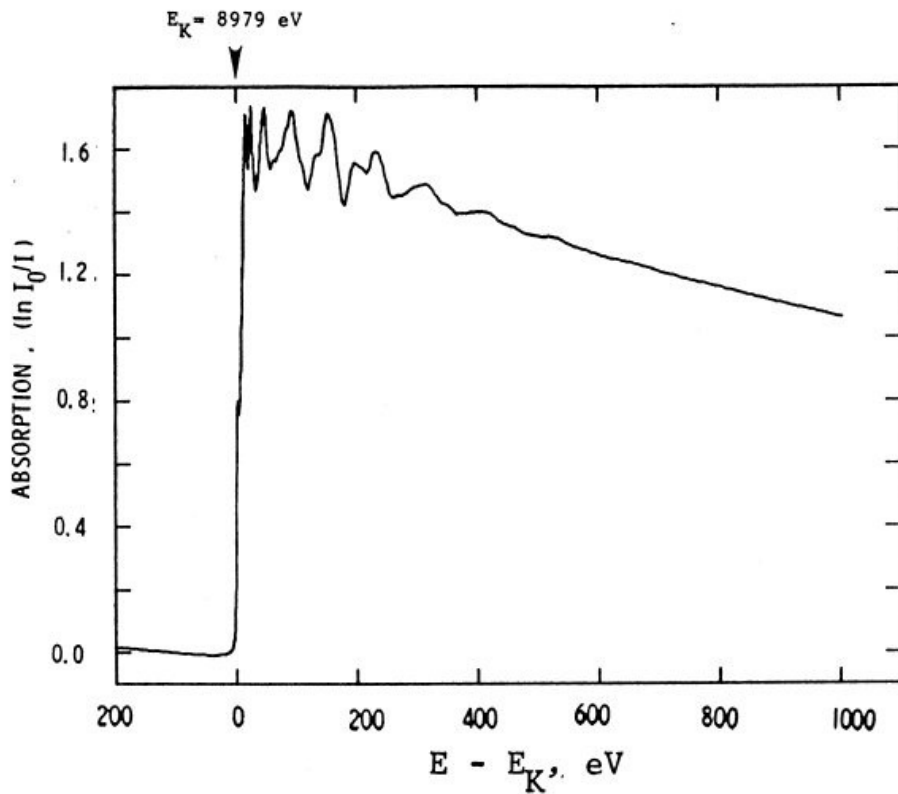




Zn

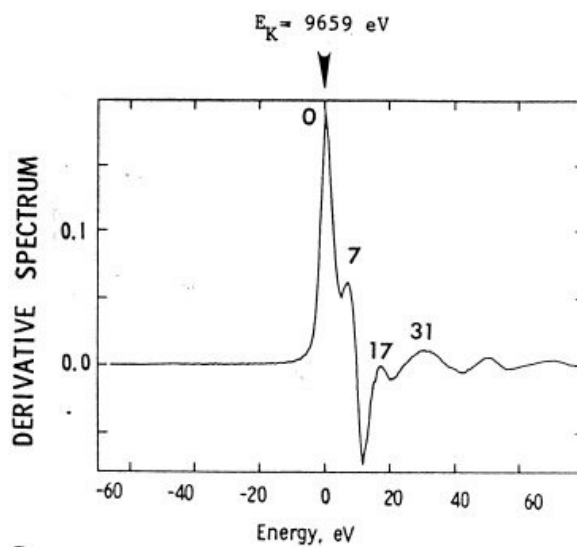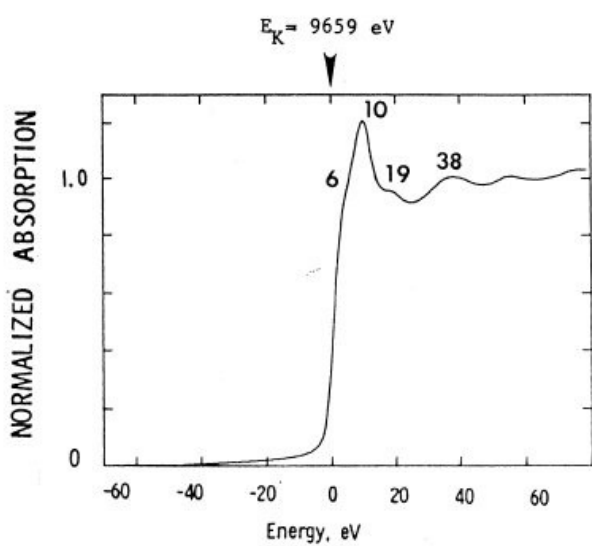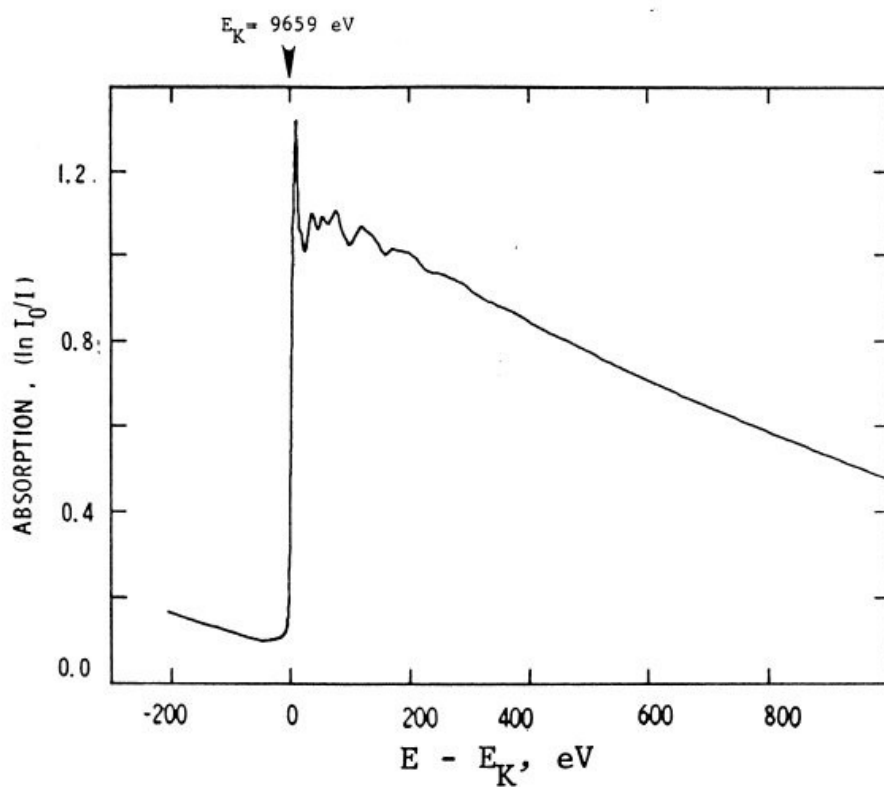




Se

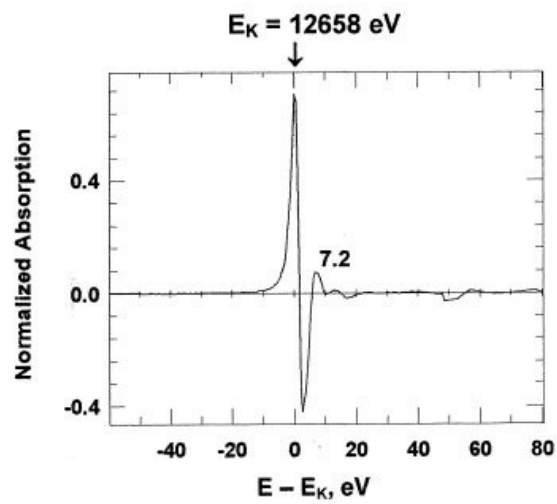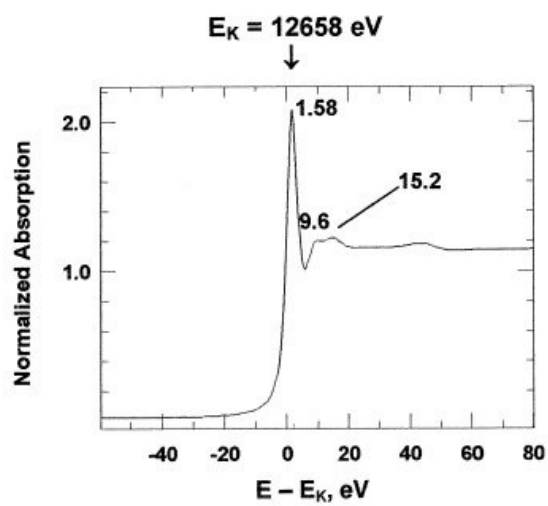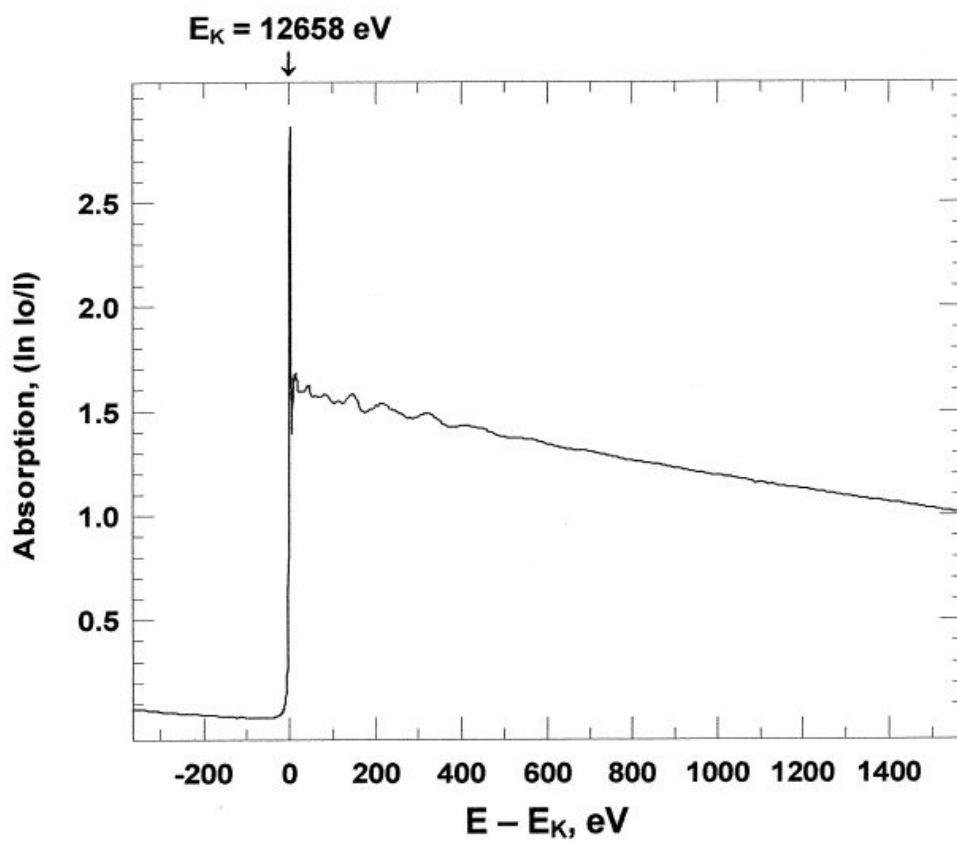




Zr

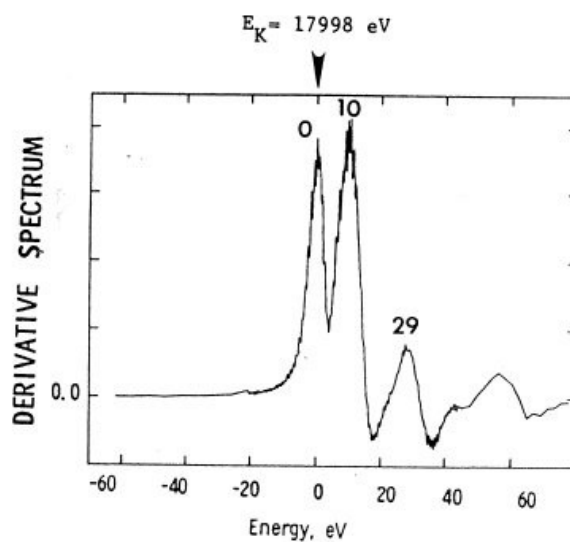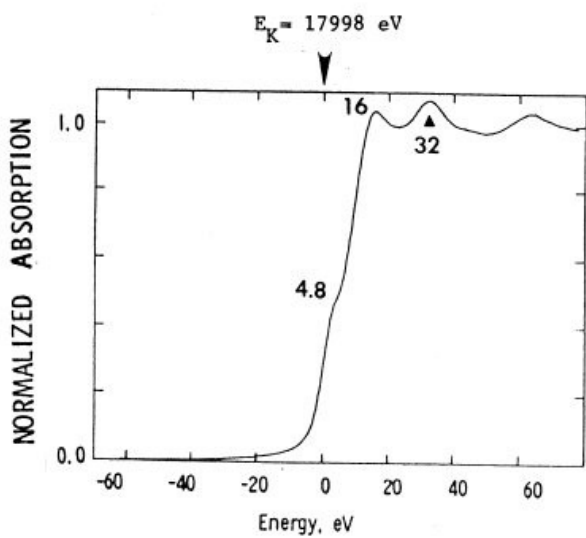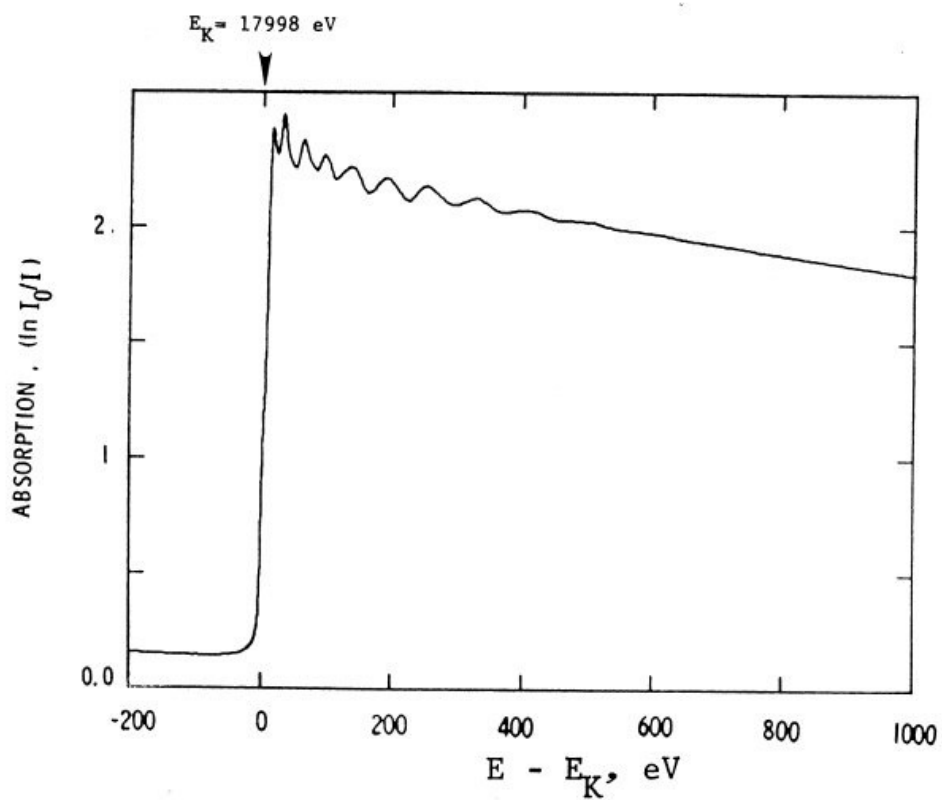




Nb

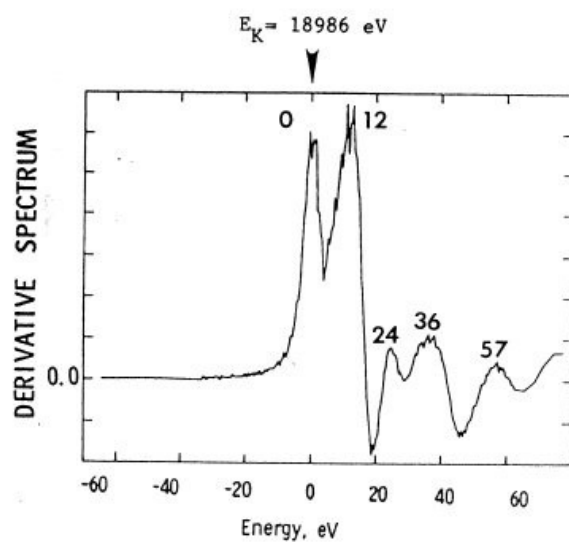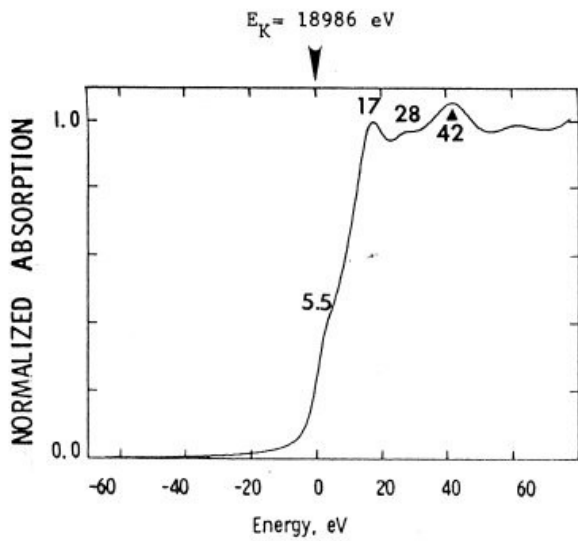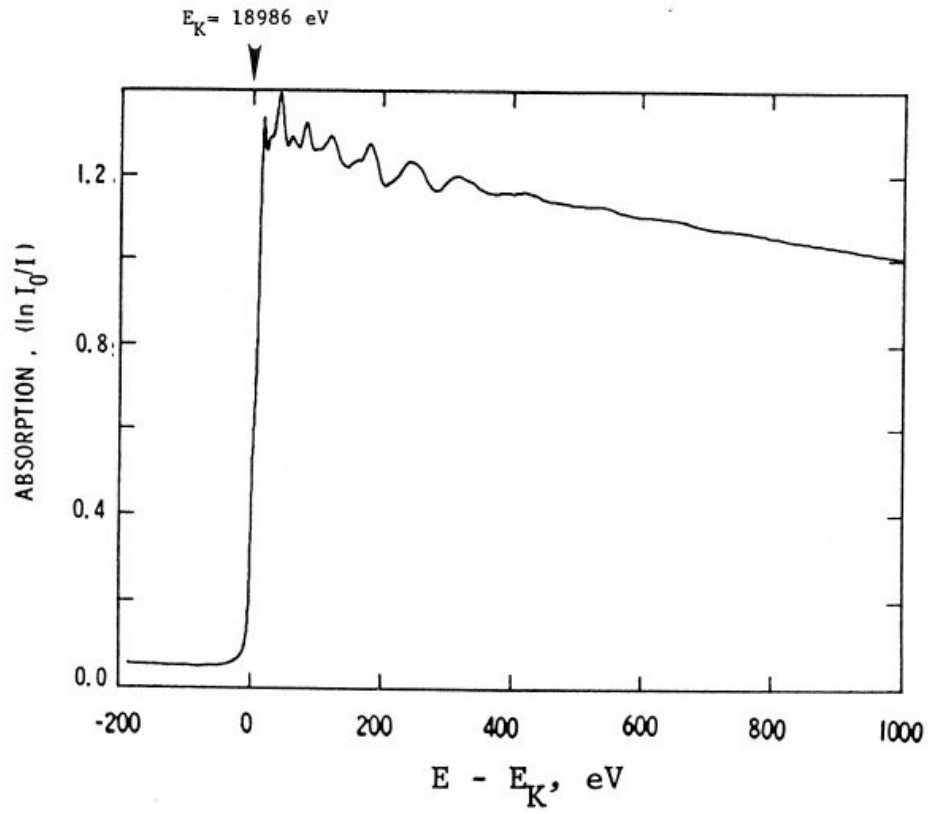

Mo

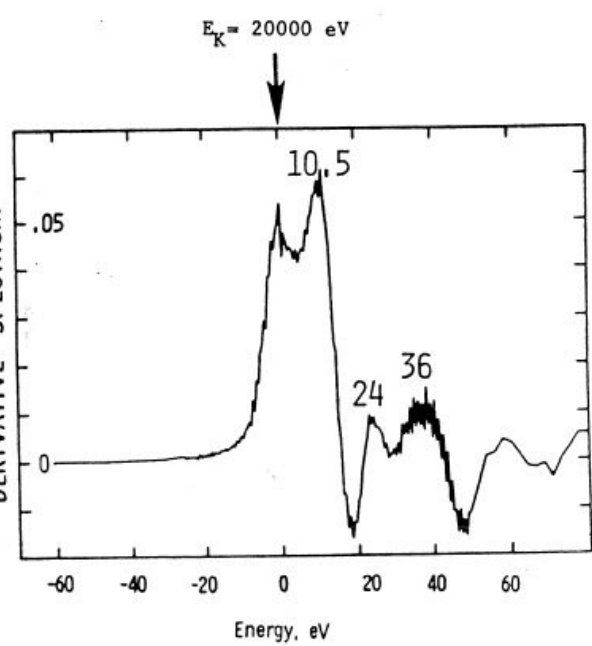
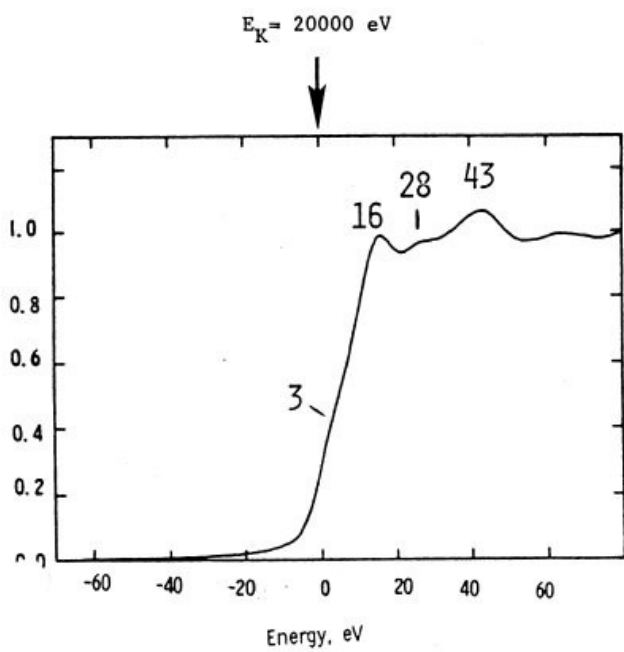
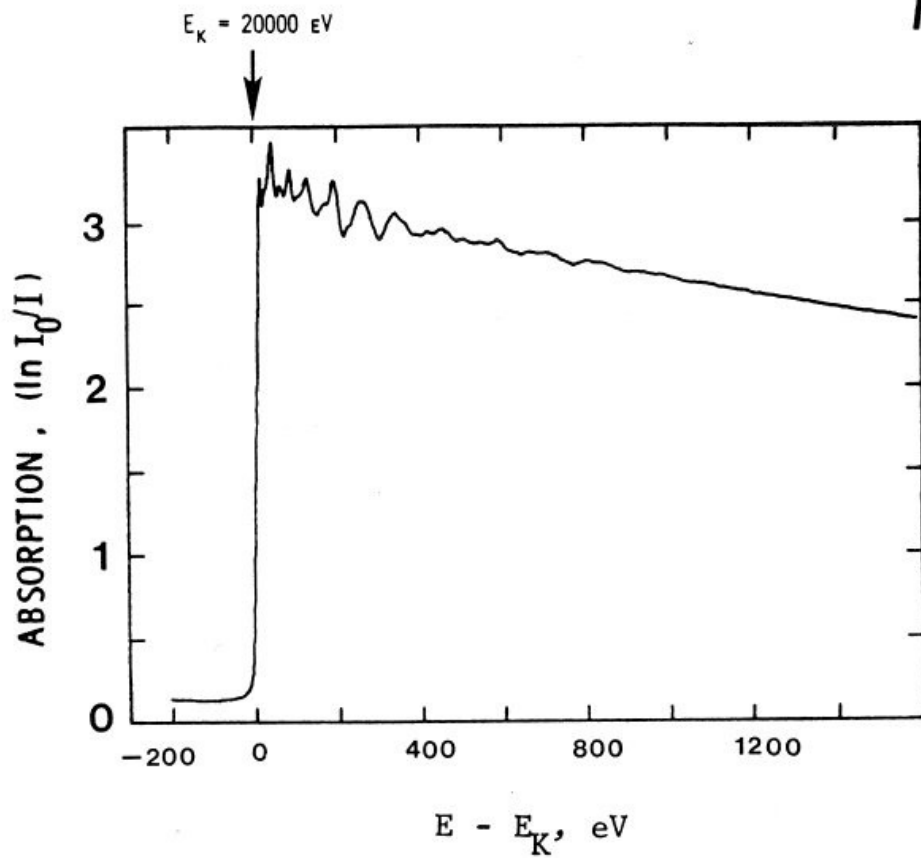


Pd

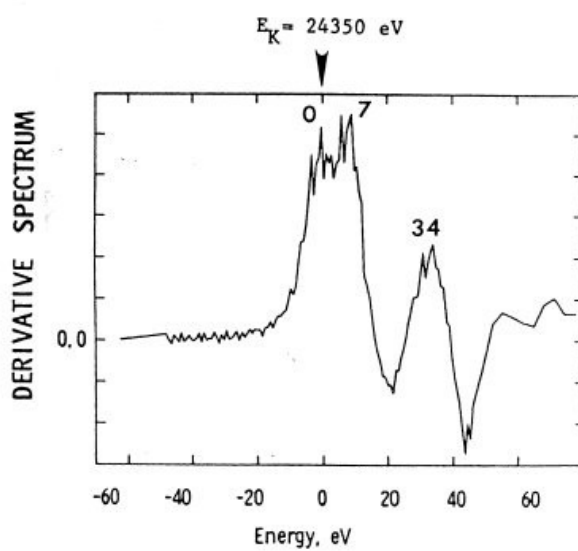
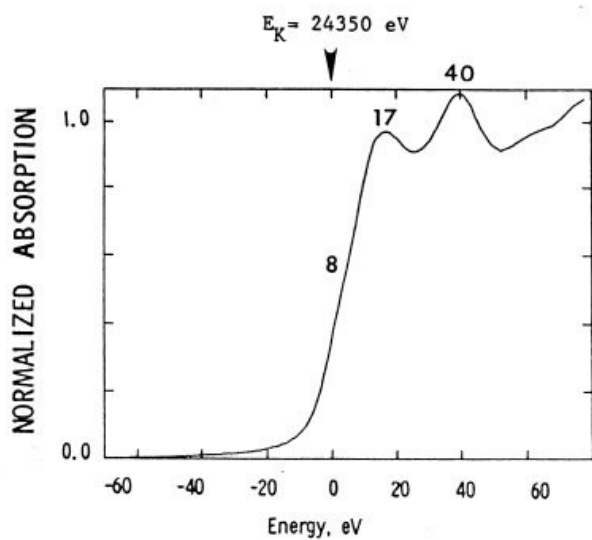
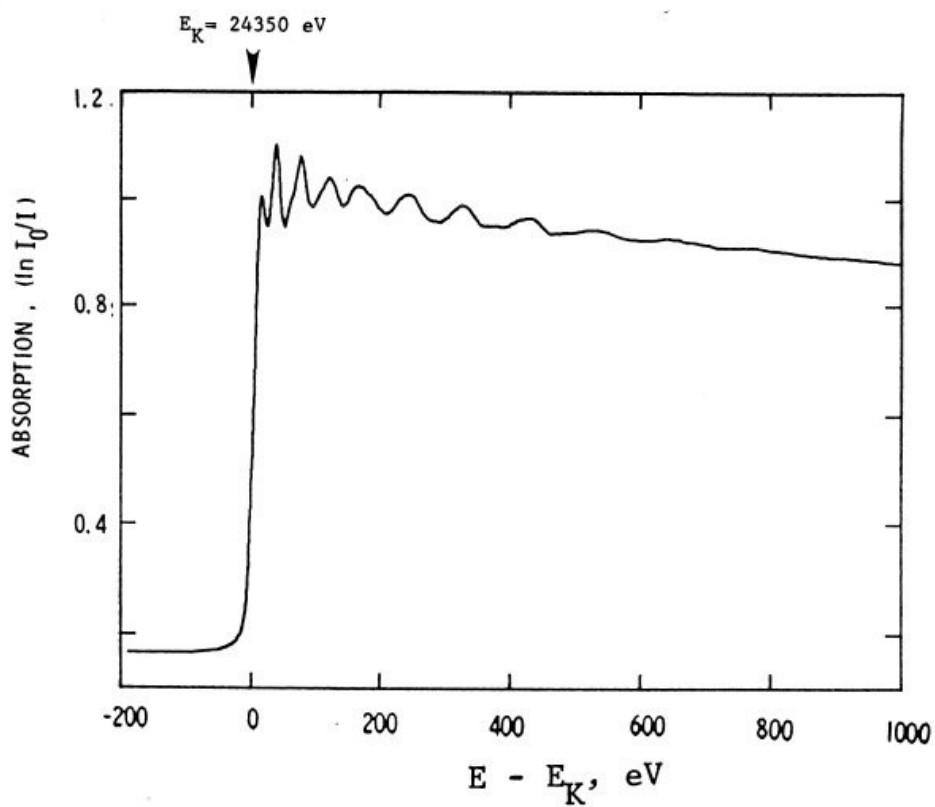




Ag

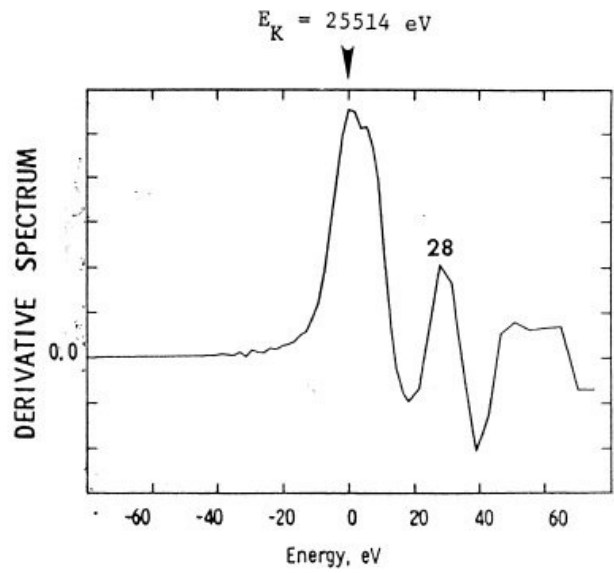
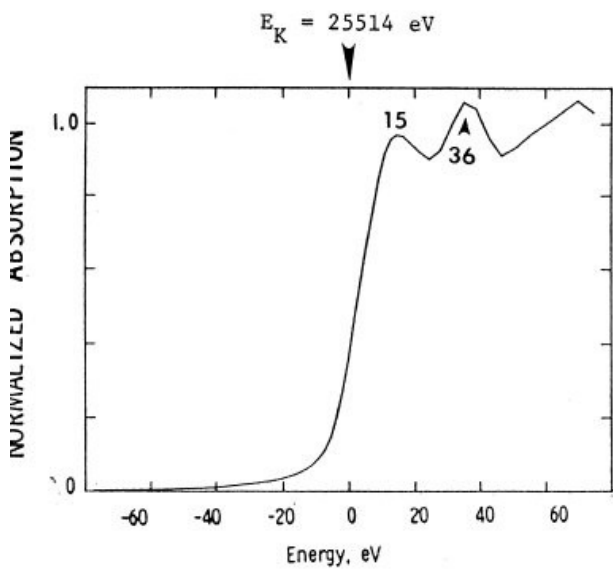
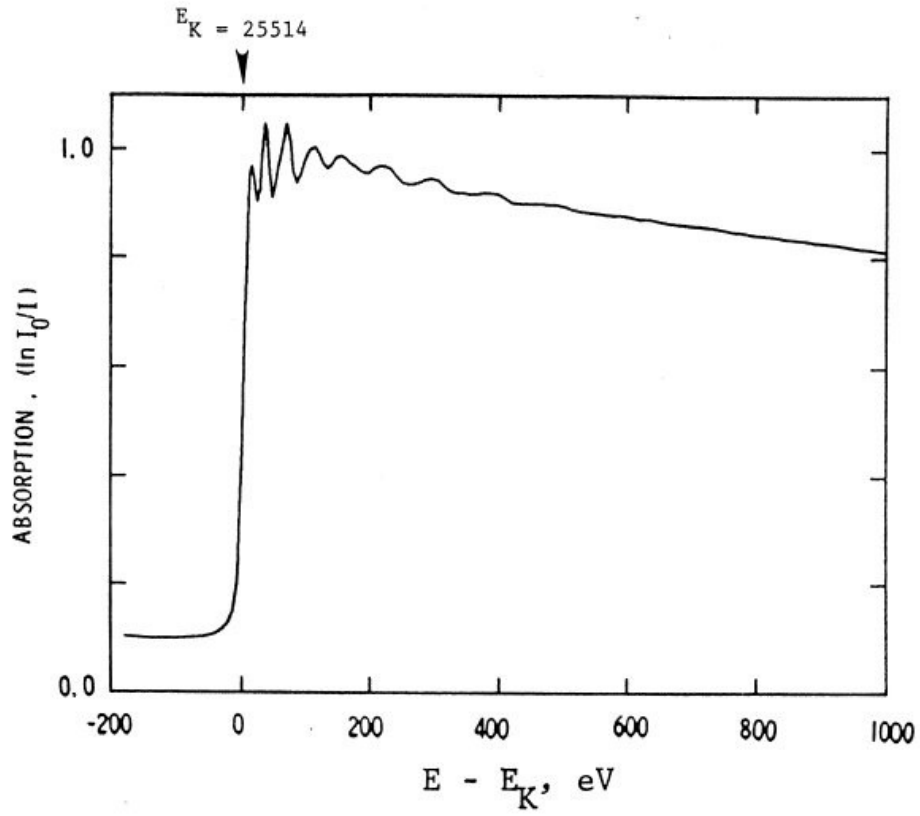


Sn

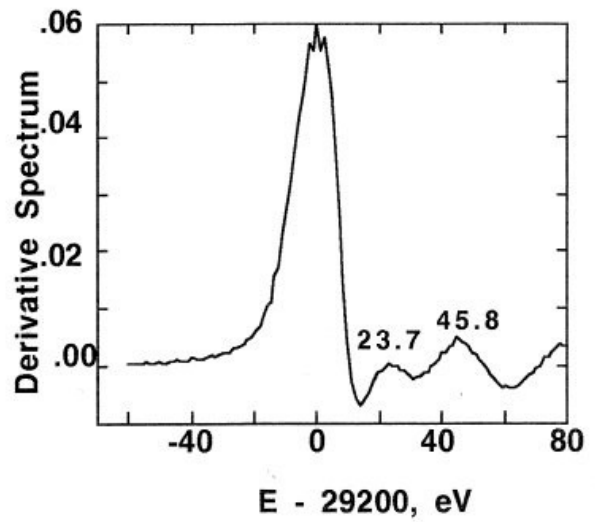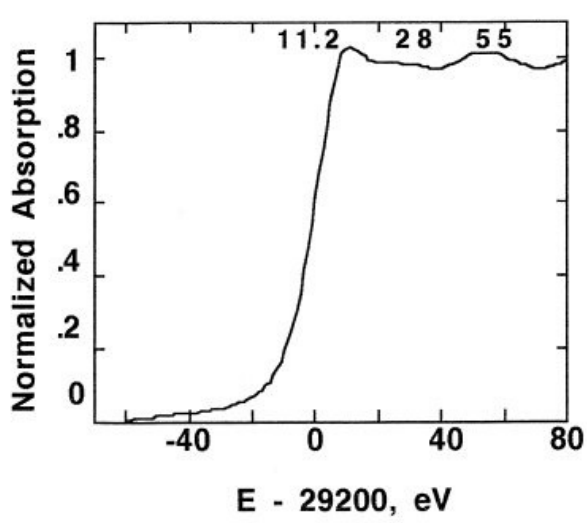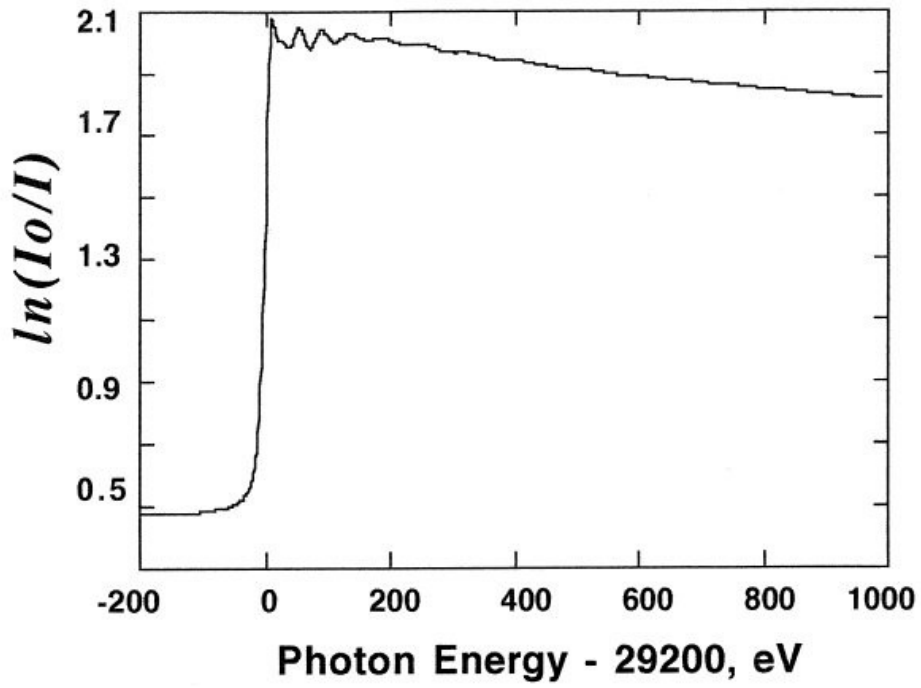




15a

Sb

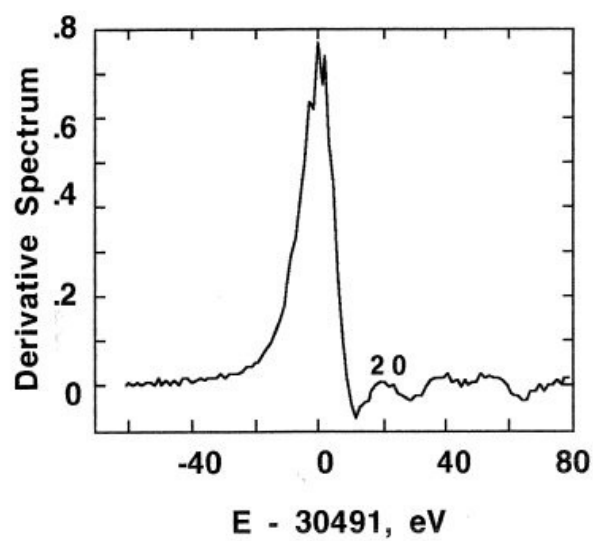
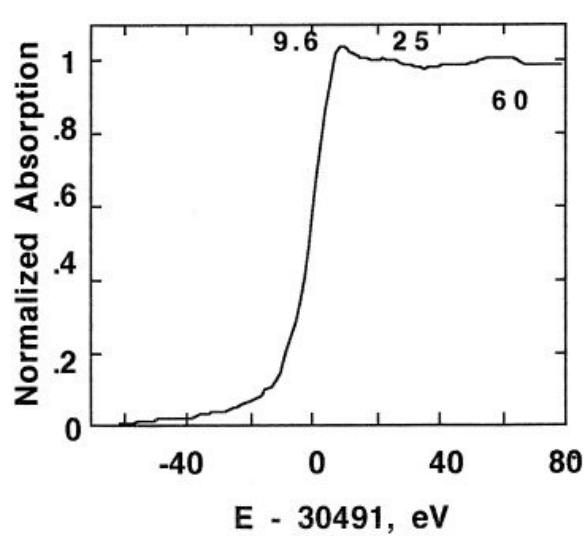
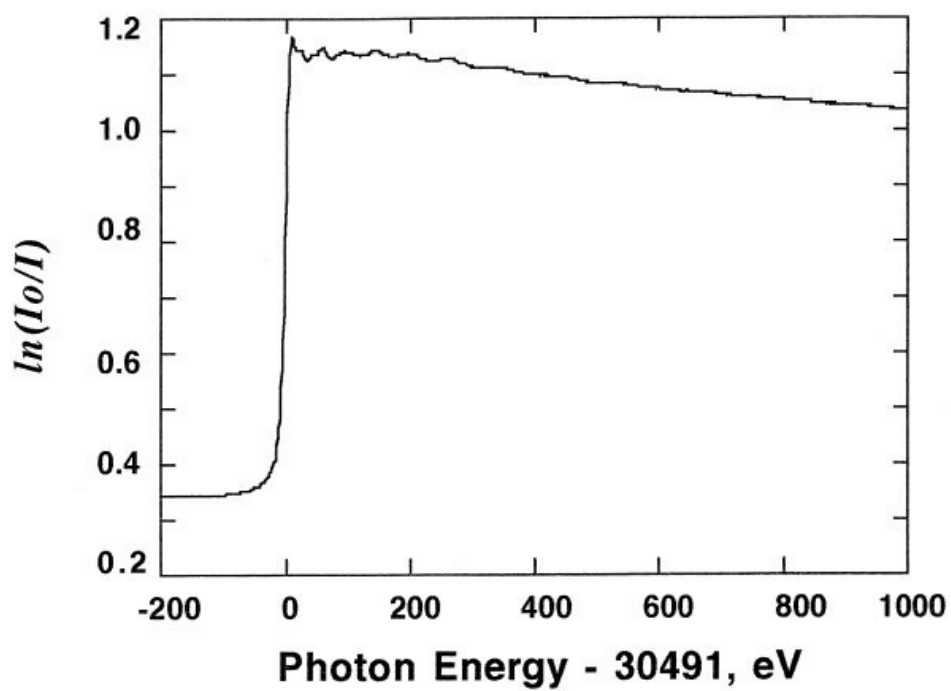


15b




Ta

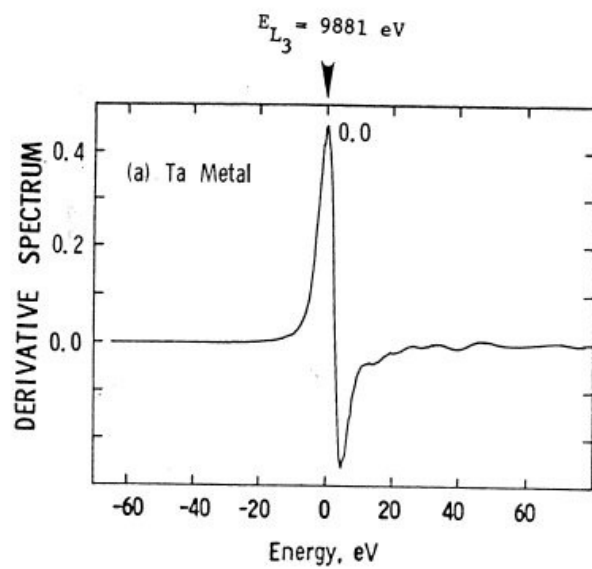
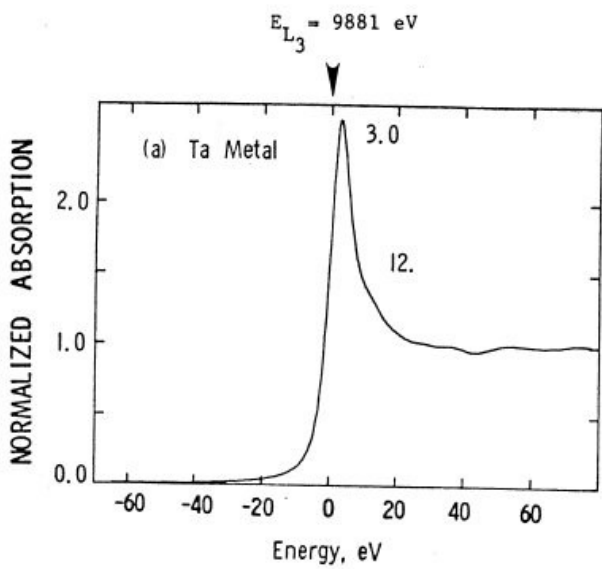
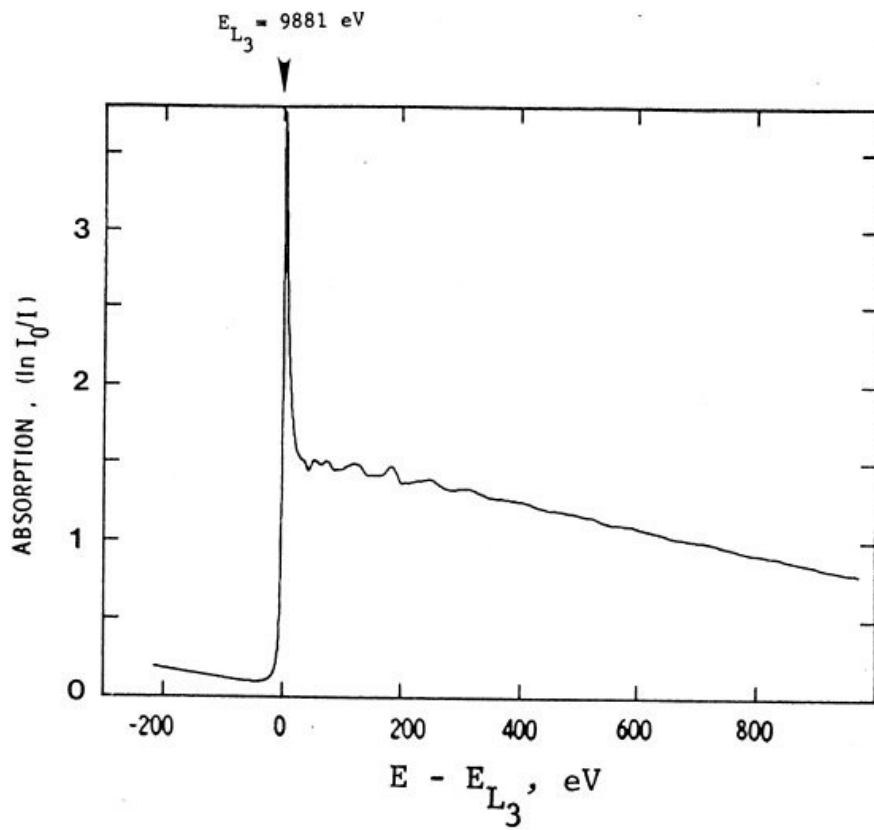


Pt

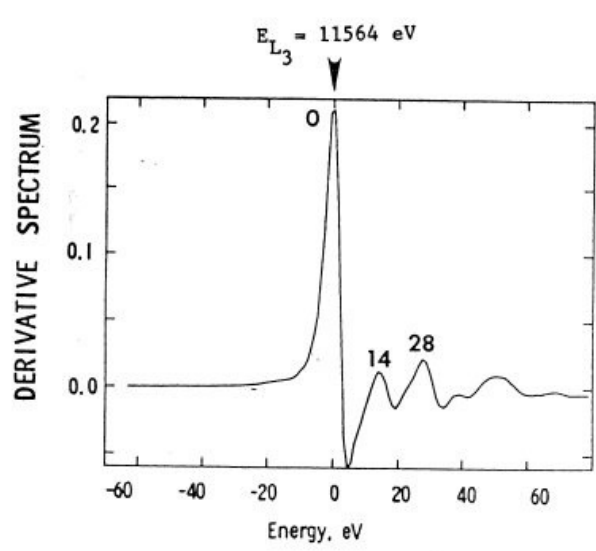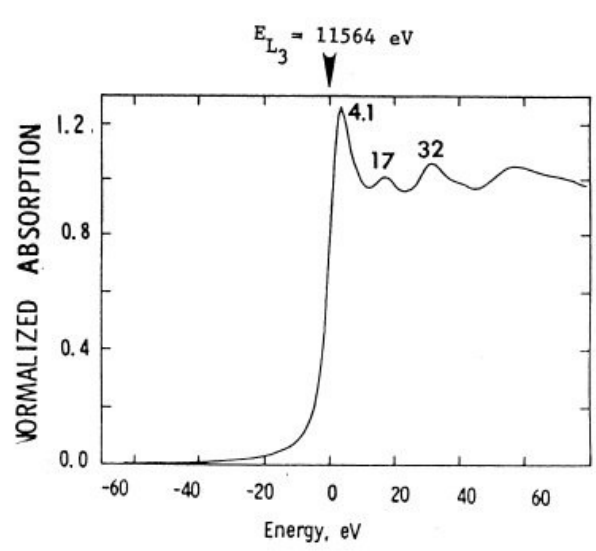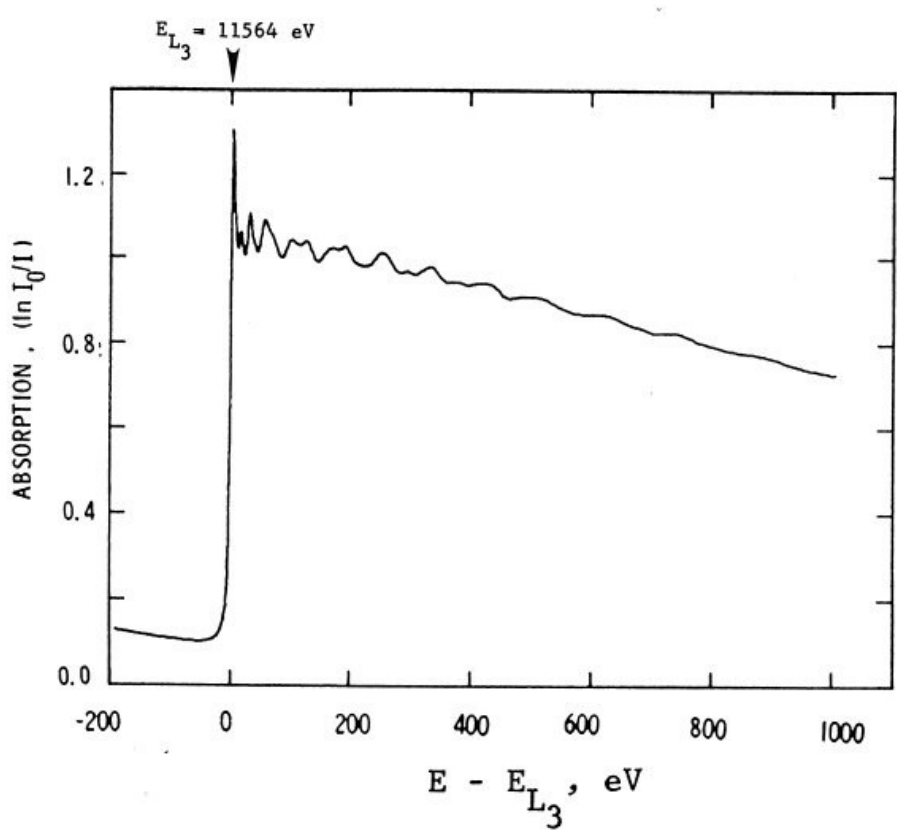

Au

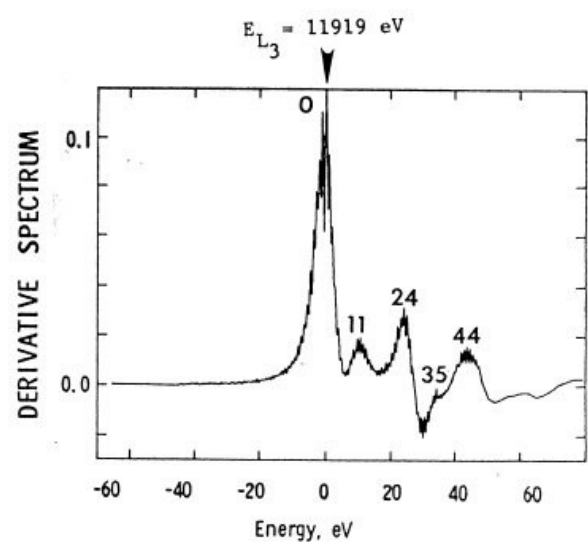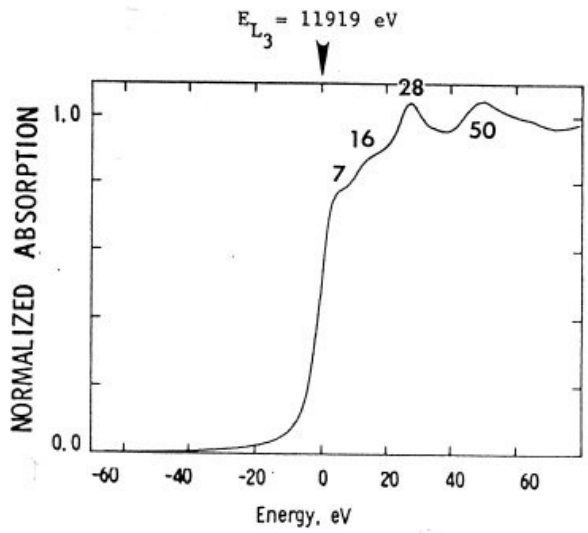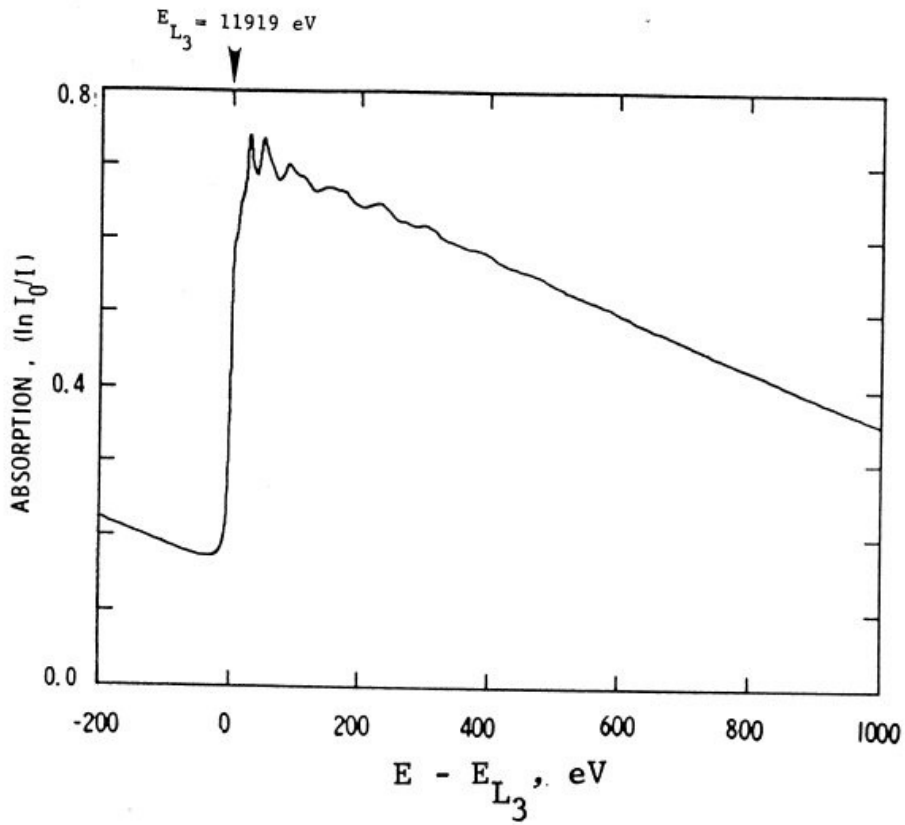

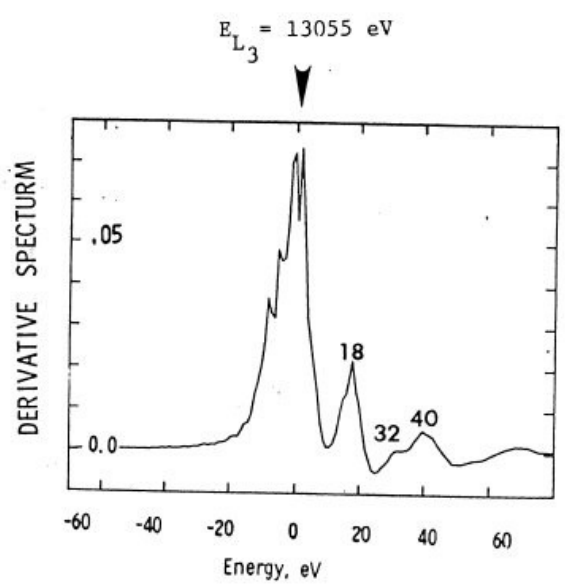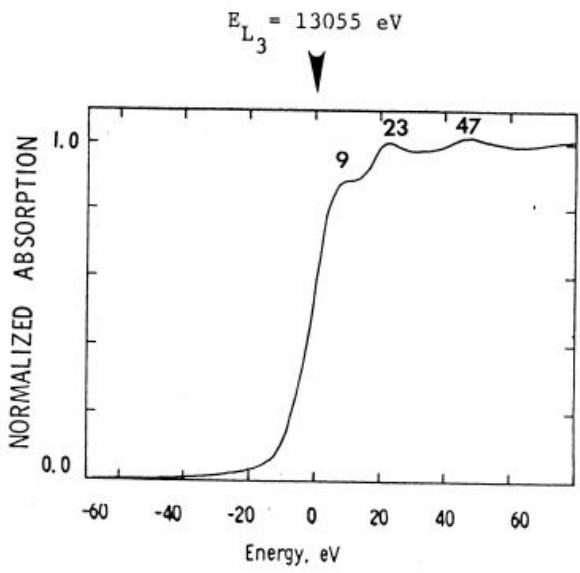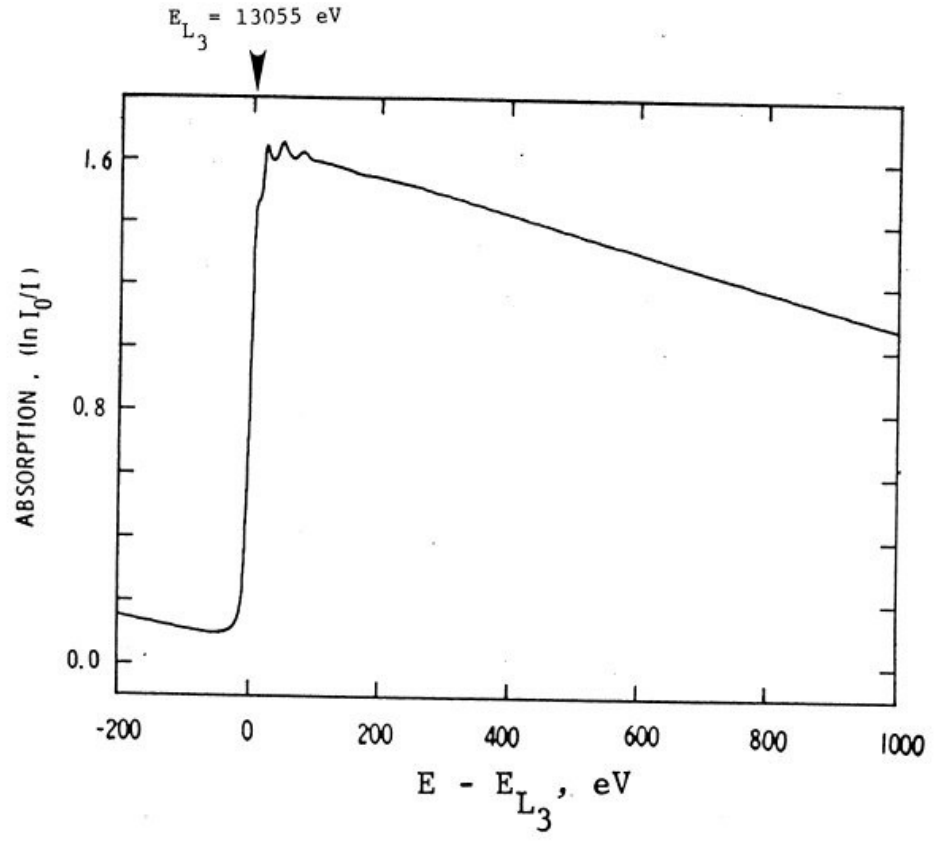

X-Ray K- and L-Edge Energies, eV					
Element	Z	K-Edge	L1	L2	L3
H	1	13.6	0.0	0.0	0.0
He	2	24.6	0.0	0.0	0.0
Li	3	54.8	0.0	0.0	0.0
Be	4	111.0	0.0	0.0	0.0
B	5	188.0	0.0	4.7	4.7
C	6	283.8	0.0	6.4	6.4
N	7	401.6	0.0	9.2	9.2
O	8	532.0	23.7	7.1	7.1
F	9	685.4	31.0	8.6	8.6
Ne	10	866.9	45.0	18.3	18.3
Na	11	1072.1	63.3	31.1	31.1
Mg	12	1305.0	89.4	51.4	51.4
Al	13	1559.6	117.7	73.1	73.1
Si	14	1838.9	148.7	99.2	99.2
P	15	2145.5	189.3	132.2	132.2
S	16	2472.0	229.2	164.8	164.8
Cl	17	2822.4	270.2	201.6	200.0
Ar	18	3202.9	320.0	247.3	245.2
K	19	3607.4	377.1	296.3	293.6
Ca	20	4038.1	437.8	350.0	346.4
Sc	21	4492.8	500.4	406.7	402.2
Ti	22	4966.4	563.7	461.5	455.5
V	23	5465.1	628.2	520.5	512.9
Cr	24	5989.2	694.6	583.7	574.5
Mn	25	6539.0	769.0	651.4	640.3
Fe	26	7112.0	846.1	721.1	708.1
Co	27	7708.9	925.6	793.8	778.6
Ni	28	8332.8	1008.1	871.9	854.7
Cu	29	8978.9	1096.1	951.0	931.1
Zn	30	9658.6	1193.6	1042.8	1019.7
Ga	31	10367.1	1297.7	1142.3	1115.4
Ge	32	11103.1	1414.3	1247.8	1216.7
As	33	11866.7	1526.5	1358.6	1323.1
Se	34	12657.8	1653.9	1476.2	1435.8
Br	35	13473.7	1782.0	1596.0	1549.9
Kr	36	14325.6	1921.0	1727.2	1674.9
Rb	37	15199.7	2065.1	1863.9	1804.4
Sr	38	16104.6	2216.3	2006.8	1939.6
Y	39	17038.4	2372.5	2155.5	2080.0
Zr	40	17997.6	2531.6	2306.7	2222.3
Nb	41	18985.6	2697.7	2464.7	2370.5
Mo	42	19999.5	2865.6	2625.1	2520.2
Tc	43	21044.0	3042.5	2793.2	2676.9
Ru	44	22117.2	3224.0	2966.9	2837.9
Rh	45	23219.9	3411.9	3146.1	3003.8
Pd	46	24350.3	3604.3	3330.3	3173.3
Ag	47	25514.0	3805.8	3523.7	3351.0
Cd	48	26711.2	4018.0	3727.0	3537.5
In	49	27939.9	4237.5	3938.0	3730.1
Sn	50	29200.1	4464.7	4156.1	3928.8
Sb	51	30491.2	4698.3	4380.4	4132.2
Te	52	31813.8	4939.2	4612.0	4341.4
I	53	33169.4	5188.1	4852.1	4557.1



X-Ray K- and L-Edge Energies, eV					
Element	Z	K-Edge	L1	L2	L3
Xe	54	34561.4	5452.8	5103.7	4782.2
Cs	55	35984.6	5714.3	5359.4	5011.9
Ba	56	37440.6	5988.8	5623.6	5247.0
La	57	38924.6	6266.3	5890.6	5482.7
Ce	58	40443.0	6548.8	6164.2	5723.4
Pr	59	41990.6	6834.8	6440.4	5964.3
Nd	60	43568.9	7126.0	6721.5	6207.9
Pm	61	45184.0	7427.9	7012.8	6459.3
Sm	62	46834.2	7736.8	7311.8	6716.2
Eu	63	48519.0	8052.0	7617.1	6976.9
Gd	64	50239.1	8375.6	7930.3	7242.8
Tb	65	51995.7	8708.0	8251.6	7514.0
Dy	66	53788.5	9045.8	8580.6	7790.1
Ho	67	55617.7	9394.2	8917.8	8071.1
Er	68	57485.5	9751.3	9264.3	8357.9
Tm	69	59389.6	10115.7	9616.9	8648.0
Yb	70	61332.3	10486.4	9978.2	8943.6
Lu	71	63313.8	10870.4	10348.6	9244.1
Hf	72	65350.8	11270.7	10739.4	9560.7
Ta	73	67416.4	11681.5	11136.1	9881.1
W	74	69525.0	12099.8	11544.0	10206.8
Re	75	71676.4	12526.7	11958.7	10535.3
Os	76	73870.8	12968.0	12385.0	10870.9
Ir	77	76111.0	13418.5	12824.1	11215.2
Pt	78	78394.8	13879.9	13272.6	11563.7
Au	79	80724.9	14352.8	13733.6	11918.7
Hg	80	83102.3	14839.3	14208.7	12283.9
Tl	81	85530.4	15346.7	14697.9	12657.5
Pb	82	88004.5	15860.8	15200.0	13035.2
Bi	83	90525.9	16387.6	15711.1	13418.6
Po	84	93105.0	16939.3	16244.3	13813.8
At	85	95729.9	17493.0	16784.7	14213.5
Rn	86	98404.0	18049.0	17337.1	14619.4
Fr	87	101137.0	18639.0	17906.5	15031.2
Ra	88	103921.9	19236.7	18484.3	15444.4
Ac	89	106755.3	19840.0	19083.2	15871.0
Th	90	109650.9	20472.1	19693.2	16300.3
Pa	91	112601.4	21104.6	20313.7	16733.1
U	92	115606.1	21757.4	20947.6	17166.3
Np	93	118678.0	22426.8	21600.5	17610.0
Pu	94	121818.0	23097.2	22266.2	18056.8
Am	95	125027.0	23772.9	22944.0	18504.1
Cm	96	128200.0	24460.0	23779.0	18930.0
Bk	97	131590.0	25275.0	24385.0	19452.0
Cf	98	135960.0	26110.0	25250.0	19930.0
Es	99	139490.0	26900.0	26020.0	20410.0
Fm	100	143090.0	27700.0	26810.0	20900.0
Md	101	146780.0	28530.0	27610.0	21390.0
No	102	150540.0	29380.0	28440.0	21880.0
Lr	103	154380.0	30240.0	29280.0	22360.0

Source: J.A.Bearden and A.F.Burr, Rev.Mod.Phys. 39, 125 (1967)  
 Tabulated by: B. Rupp and Joe Wong